

## Preparation of Calcium Phosphate Via Precipitation Technique

**Dr. Wafaa A. Hussain**

Applied Sciences Department, University of Technology/Baghdad.

Email:wafaloay@yahoo.com

**Luay H. Alwan**

Applied Sciences Department, University of Technology/Baghdad.

Received on:22/4/2014 & Accepted on:5/3/2015

### ABSTRACT:

Recently, there has been an increasing attention on the preparation of calcium phosphates CaP for the development, understanding and manufacturing of biomaterials. In this study, precipitation process was performed to prepare calcium phosphates powders by varying the Ca/P molar ratio as (1.54, 1.67 and 1.8). Calcium acetate was added to disodium hydrogen phosphate, the precipitate was left overnight and dried at 100°C and then the powder was treated at 900°C for 1 hour. The powder sample was evaluated using such as scanning electron microscope (SEM), X-ray diffraction (XRD), atomic force molecules (AFM) and Fourier Transform Infrared (FTIR). It can be concluded, it is possible to synthesis hydroxyapatite (HA) and biphasic calcium phosphate (BCP) powders with nano particle.

**Keywords:** calcium phosphates, Precipitation technique

### تحضير فوسفات الكالسيوم بتقنية الترسيب

#### الخلاصة

ازداد الاهتمام في الوقت الحاضر في تحضير فوسفات الكالسيوم لتطوير و فهم وصناعة المواد الحيوية. في هذه الدراسة تم تنفيذ عملية الترسيب لتحضير مساحيق فوسفات الكالسيوم وذلك بتغيير النسبة المولية للكالسيوم الى الفوسفات (1.54 و 1.67 و 1.8). تم إضافة استينات الكالسيوم إلى فوسفات هيدروجين ثنائي الصوديوم, ترك الراسب ليلة كاملة وجفف عند 100 °م وبعدها تم معاملة المسحوق عند 900 °م لمدة ساعة. قيمت عينة المسحوق باستخدام المجهر الإلكتروني الماسح و حيود الأشعة السينية و جزيئات القوة الذرية و مطيافية الأشعة تحت الحمراء. يمكن الاستنتاج انه من الممكن تصنيع مساحيق هابيدروكسيابتايت و فوسفات الكالسيوم ثنائي الطور بجسيمات نانوية.

### INTRODUCTION:

Ceramics are thermal and chemical stability, high strength, wear resistance and durable, all these make ceramics good candidate materials for surgical implants. Ceramic materials that are specially developed for use as medical and dental implants are termed bioceramics. Bioceramics can have structural functions as joint or tissue replacements because they exhibit biological affinity and activity to surrounding host tissues, which can be used as coatings to improve the biocompatibility and corrosion resistance of metal implants, and can function as resorbable lattice, which provide temporary structures and a framework that is dissolved, replaced as the body rebuilds tissue [1,2].

For many years, biodegradable implants have been thought to offer advantages over metal analogs. In orthopedic practice, metal implants can distort magnetic resonance imaging (MRI), and they release metal ions into the surrounding tissue. Further disadvantages include the need for a second surgical procedure for implant removal and complicated revision surgery resulting from the presence of the implant [3].

Bioceramics can fall into three biomaterial classification: inert, resorbable and active, meaning they can either remain unchanged, dissolve or actively take part in physiological processes [4].

Calcium phosphates CaP are broadly used in medicine and oral biology due to the apatite-like structure of enamel, dentin and bones, usually called "hard tissues" [5]. There are several calcium phosphates CaP ceramics that are most frequently used in the biomaterial field such as, hydroxyapatite (HA)  $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$ , tricalcium phosphate (TCP)  $\text{Ca}_3(\text{PO}_4)_2$ , dicalcium phosphate dihydrate (brushite)  $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$ , dicalcium phosphate (DCP)  $\text{CaHPO}_4$ , octacalcium phosphate (OCP)  $\text{Ca}_8\text{H}_2(\text{PO}_4)_6 \cdot 5\text{H}_2\text{O}$  and tetracalcium phosphate  $\text{Ca}_4\text{P}_2\text{O}_9$  [6,7].

Bioactive materials TCP and HA cause a positive reaction after implantation in terms of bony tissue formation, strengthening or interlocking which in turn promotes regeneration of the bone and its function. Bioactivity of CaP materials is dependent on many factors during the synthesis procedure, such as precursor reagents, impurity contents, crystal size and morphology, concentration and mixture order of reagents, pH and temperature. Also, the bioactivity response of Ca-P materials will depend on thermal treatment profile for drying and sintering. These conditions are controlled by synthesis preparation parameters and consequently for each application a specific route is selected [8].

Various processes for the preparation of HA powders have been developed over the past decades including wet synthesis, solid-state reaction [9], hydrothermal methods [10], sol-gel process [11] etc. The initial purpose of these processes is to produce HA powders which demonstrate desired characteristics, for example high specific surface area, fine grain size and size distribution including small in particle agglomeration. In particular, wet-chemical precipitation route is the most talented route owing to its ease in experiment operations, low working temperature, high percentages of pure products and inexpensive equipment requirement [5].

In order to gain insights into the complex structure found in biological mineral phases there would be required a well-defined characterization of the synthetic Ca-P, where the composition, crystallinity and nanostructure have to be properly addressed. These properties play a major role on the bioactivity of Ca-P based materials in terms of enhanced contact areas and degradation. In the present study, we aimed to synthesize calcium phosphate powders by wet precipitation technique in three different Ca:P molar ratio. The treated precipitation powder characterized by scanning electron microscopy (SEM), X-ray diffraction (XRD), atomic force molecules (AFM) and Fourier Transform Infrared Spectroscopy (FTIR).




## Materials and methods:

### Materials and synthesis

The starting materials include: Calcium acetate ( $\text{Ca}(\text{AC})_2$ ) (BDH Limited poole England) and disodium hydrogen phosphate ( $\text{Na}_2\text{HPO}_4$ ) (BDH Limited poole England). Distilled water was used in all synthesis steps.

A solution of disodium hydrogen phosphate ( $\text{Na}_2\text{HPO}_4$ ) of 0.015 M was dissolved in distilled water (150 ml), and a solution of calcium acetate ( $\text{Ca}(\text{AC})_2$ ) of 0.023,

0.025 and 0.027 M was also dissolved in distilled water (250) ml in Ca:P molar ratio (1.54 MR<sub>1</sub>, 1.67 MR<sub>2</sub> and 1.8 MR<sub>3</sub>). A solution of calcium acetate added drop by drop to the boiling disodium hydrogen phosphate solution [12]. The obtained precipitations can be described by Equations [13].



The precipitate was aged overnight at room temperature, washed with distilled water, filtered by using filter paper and dried at 100 °C. The dried powder was crushed by using mortar and pestle then calcined in alumina crucible at 900°C for one hour in air atmosphere at the rate of 5°C/min.

### Characterization

Scanning electron microscopy was performed to determine microstructure of the resulting powders after heat treatment. CaP powders were analyzed by X-ray diffraction (XRD) with Siemens-Brucker D5000 diffractometer. This instrument works with voltage and current settings of 40 KV and 30 mA, respectively, and uses Cu-K $\alpha$  radiation (1.54060 Å). Scanning speed 5 deg/min, scan mode: continuous scan. The particle size analysis of CaP was done by atomic force microscopy (AFM). Scanning probe microscope (CSPM-5000) as instrument was used for this analysis. Fourier transform infra red (FTIR) spectrum of synthesized CaP powder was obtained over the wave numbers 400-4000 cm<sup>-1</sup>. The powder was dispersed into pellets of KBr (mixed in 1:4 ratios).

### Results and discussion:

#### SEM analysis

SEM micrograph of the CaP powder obtained from MR<sub>3</sub> after heat-treatment is shown in Figure (1). The figures show the precipitation powder with different magnification, from the figures it can be found a homogeneous microstructure with ellipsoidal grains with 93 nm average diameter.

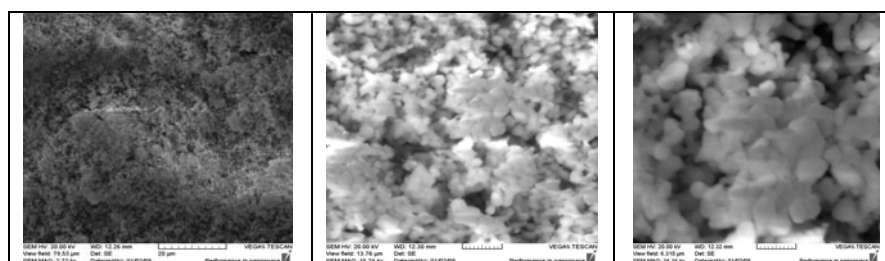


Figure (1) SEM images of the powder obtained from MR<sub>3</sub>

**XRD analysis**

Characterization of the obtained powder after heat treatment was done with XRD. The straight base line and the sharp peaks of the diffractogram in Figures (2,3 and 4) confirmed that the product was well crystallized.

If the Ca/P molar ratio is lower than 1.67 ( $MR_1$ ), then beta tricalcium phosphate  $Ca_3(PO_4)_2$  present as a main phase and traces of HA were also detected at the XRD patterns as shown in Fig.(2). Mixtures of HA and TCP, known as biphasic calcium phosphate (BCP), have been investigated as bone substitutes.

The stoichiometric ratio (1.67)  $MR_2$  expected a pure HA phase as shown in Fig. (3).

When the Ca/P molar ratio is 1.8 ( $MR_3$ ), the XRD patterns indicated that hydroxyapatite HA was formed in this sample as a main phase and traces of CaO were also detected as shown in Fig.(4).

These extraneous phases may adversely affect the biological response to the implant in vivo. In certain circumstances it might be desirable for an implant to assist in bone repair and then be slowly resorbed and replaced by natural tissue. However, it is necessary to match the rate of resorption with that of the expected bone tissue regeneration. When the solubility of a calcium phosphate is higher than the rate of tissue regeneration, it will only be limited use in bone cavity and defect filling [14].

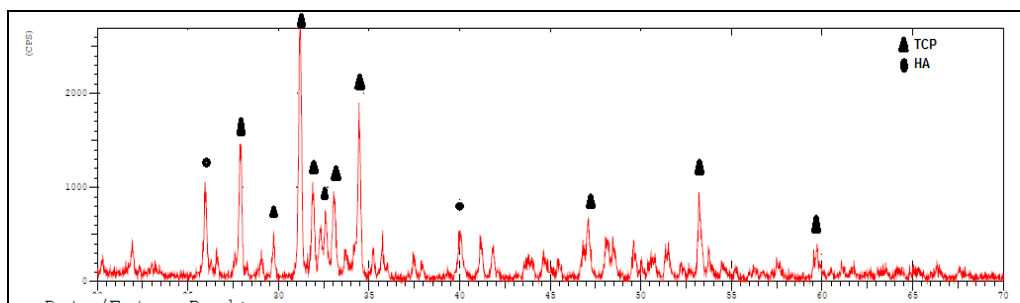


Figure (2) X-ray pattern of sample  $MR_1$

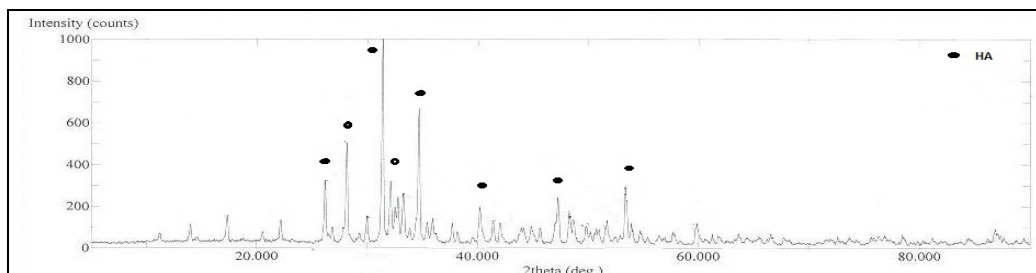


Figure (3) X-ray pattern of sample  $MR_2$

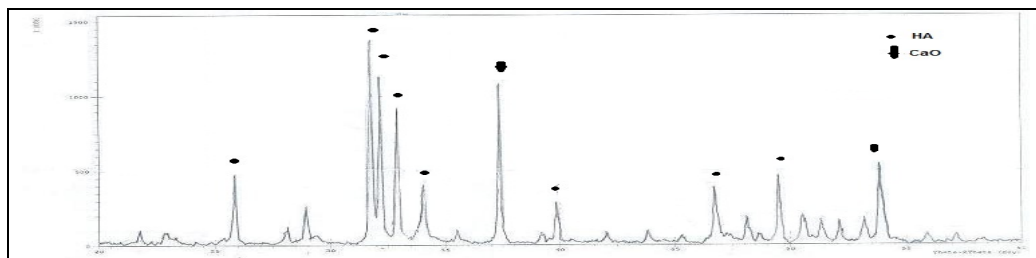


Figure (4) X-ray pattern of sample  $MR_3$

### Atomic Force Microscopy (AFM)

AFM provides nanometer-scale information about surface structure. The AFM images of the surface topography of CaP particles are shown in Figure (5, 6 and 7) for samples prepared in the three different Ca:P molar ratios. The size of the particles was determined from the AFM images. The nanoparticles were anisotropic with ellipsoidal geometry this can be seen from 3-D images on the right. While average diameter of the three powders are 90.59 nm, 111.22 nm, and 93.42 nm for MR<sub>1</sub>, MR<sub>2</sub> and MR<sub>3</sub> samples respectively were determined from particle distribution images on the left.

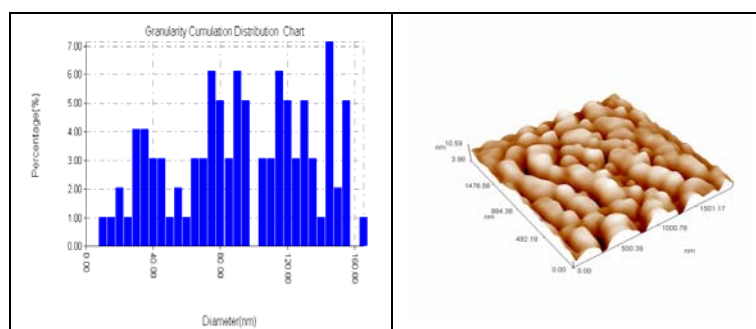


Figure (5) AFM images of sample MR<sub>1</sub>.

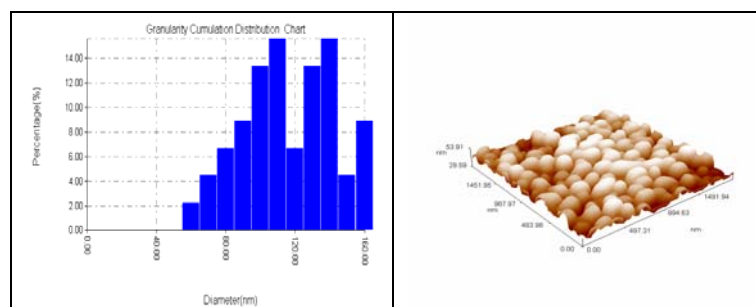


Figure (6) AFM images of sample MR<sub>2</sub>.

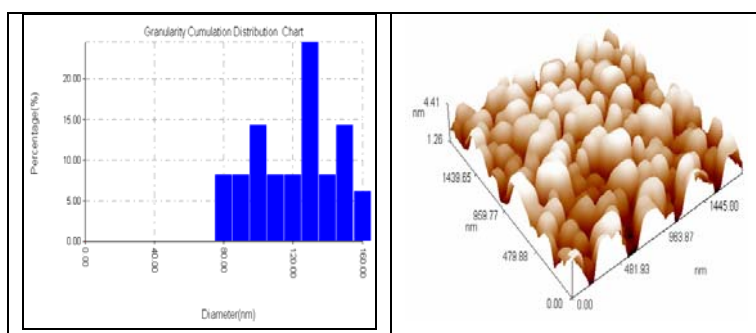


Figure (7) AFM images of sample MR<sub>3</sub>.


### FTIR analysis

Infrared characterization was carried out for the sample to study the spectral characteristics indicative of the chemical bonding in the synthesized CaP powder. The most characteristic chemical groups in the FTIR spectrum of synthesized HA are PO<sub>4</sub><sup>3-</sup>, OH<sup>-</sup>, and CO<sub>3</sub><sup>2-</sup> in the three molar ratio MR<sub>1</sub>, MR<sub>2</sub> and MR<sub>3</sub> as shown in the


figures (8, 9, and 10) respectively.  $\text{PO}_4^{3-}$  group forms intensive IR transmission bands at  $561$  and  $601\text{ cm}^{-1}$  (characteristic to TCP) for  $\text{MR}_1$ ,  $543$  and  $605\text{ cm}^{-1}$  for  $\text{MR}_2$ , and  $570$  and  $603\text{ cm}^{-1}$  for  $\text{MR}_3$  and at  $1000 - 1100\text{ cm}^{-1}$  for the three ratios.  $\text{OH}^-$  group is relatively wide, from  $3600$  to  $2600\text{ cm}^{-1}$ , a weak peak is formed at  $632\text{ cm}^{-1}$  for  $\text{MR}_3$  and additional  $\text{OH}^-$  peak appears at  $3644\text{ cm}^{-1}$ , which means that there is a  $\text{CaO}$  in the powder.  $\text{CaO}$  content is proven by presence intensive peak of  $\text{CO}_3^{2-}$  group as shown in figure 10 [15].  $\text{CO}_3^{2-}$  group forms weak and intensive peaks as shown in Figures (8, 9, and 10). Transmission bands of chemical bonds of the synthesized CaP spectrum are summarized in Table 1.

**Table 1: Transmission bands of synthesized CaP chemical groups ( $\text{cm}^{-1}$ )**

	$\text{MR}_1$	$\text{MR}_2$	$\text{MR}_3$
$\text{PO}_4^{3-}$	561,601, 1028	543,605,1008,1020,1030,1037,1085, 1068,1072,1084,1093,1116	472, 570, 603, 960,1030,1050,1091
$\text{OH}^-$	3429	3435, 3595	632, 3572, 3674
$\text{CO}_3^{2-}$	869,1653	1647,2368	873, 1413, 1460, 1990

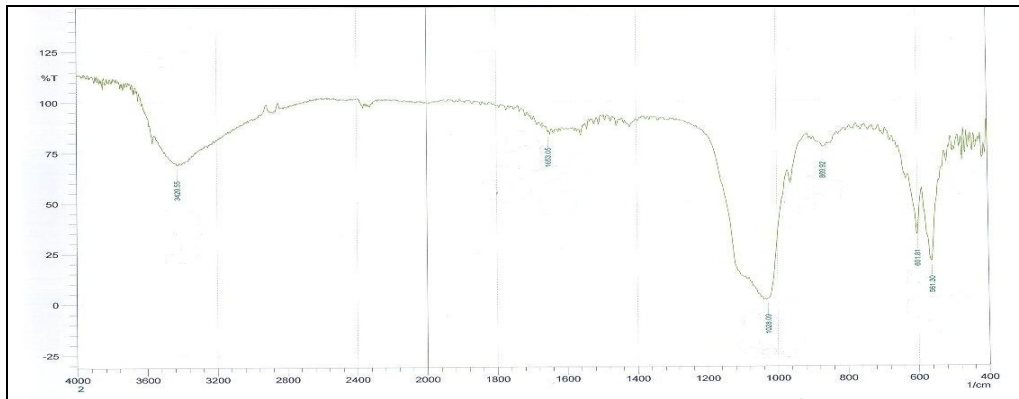

**Figure (8) The FT-IR spectra of sample  $\text{MR}_1$ .**

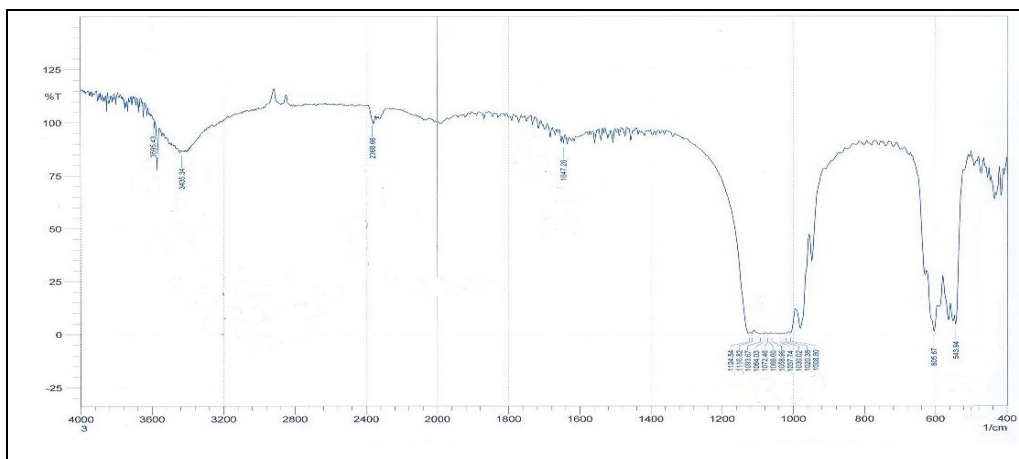

**Figure (9) The FT-IR spectra of sample  $\text{MR}_2$ .**

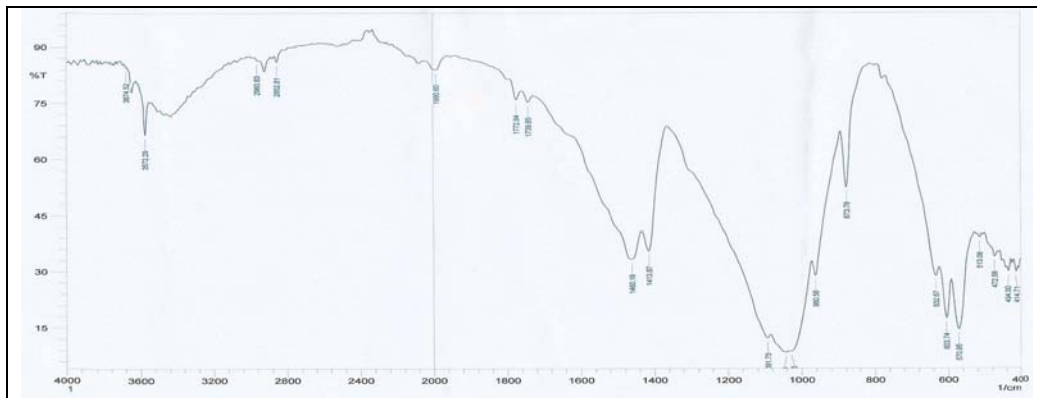


Figure (10) The FT-IR spectra of sample MR<sub>3</sub>.

### CONCLUSION:

For this study the wet-chemical precipitation could be the optimized process to induce the formation of hydroxyapatite rather than biphasic calcium phosphate, a nano grain size can be achieved by using this route.

Some secondary phases are formed during calcium phosphate process depend on original Ca/P ratio.

### REFERENCES:

- [1] Kahtan Khalaf, Waleed Asim and Payman Suhbat, "Effect of sintering temperature on some physical and mechanical properties of fabricated hydroxyapatite used for hard tissue healing", Eng. and Tech. Journal, Vol. 28, No. 10, 2010, pp: 1880-1892.
- [2] Beganskiene A. , Dudko O., Sirutkaitis R., Giraitis R., "Water based sol-gel synthesis of hydroxyapatite", Materials Science, Vol. 9, No.4, 2003, pp: 383-386.
- [3] Andreas W., Reinhard F. G., Andreas C. S., Hanns-Joachim H., and Norbert P.S., "Biodegradable implants in sports medicine: the biological base", , Vol. 16, No. 3, 2000, pp: 305-321.
- [4] Robert A. Horowitz, Ziv Mazor, Chritian Foitzik, Hari Prasad, Michael Rohrer and Ady Palti, "β- tricalcium phosphate as bone substitute material: properties and clinical applications", The International of Dental Implants and Biomaterials, Vol.1, No.2, 2009.
- [5] Naruporn MONMATURAPOJ, "Nano-size Hydroxyapatite Powders Preparation by Wet-Chemical Precipitation Route", Journal of Metals, Materials and Minerals, Vol.18 No.1, 2008, pp:15-20.
- [6] Guzm'an V'azquez C., Pi~na Barba C., and Mungu'ia N., " Stoichiometric hydroxyapatite obtained by precipitation and sol gel processes", Revista Mexicana De Fi'sica, Vol.51, No. 3, JUNIO 2005, pp: 284-293.
- [7] Amit Desai Y., "Fabrication and Characterization of Titanium-doped Hydroxyapatite Thin Films", Department of Materials Science & Metallurgy, M.sc Thesis, University of Cambridge, UK, 2007.
- [8] Maria Helena Santos, Marise de Oliveira, Luciana Palhares de Freitas Souza, Herman Sander Mansur, and Wander Luiz Vasconcelos, "Synthesis Control and Characterization of Hydroxyapatite Prepared by Wet Precipitation Process", Materials Research, Vol. 7 , N o. 4, 2004, pp: 625-630.
- [9] Ramachandra Rao R., Roopa H.N., and Kannan T.S., " Solid state synthesis and thermal stability of HAP and HAP – β-TCP composite ceramic powders" J. Mater. Sci. Mater. Med. Vol.8, Issue 8, 1997, pp: 511-518.

- [10]. Liu H.S., Chin T.S., Lai L.S., Chiu S.Y., Chung K.H., Chang C.S., and Lui M.T., "Hydroxyapatite synthesized by a simplified hydrothermal method", *Ceram. Int.* Vol.23, Issue 1, 1997, pp: 19-25.
- [11] Predoi D., Vatasescu-Balcana R.A., Pasuk I., Truscab R., and Costache M., "Calcium phosphate ceramics for biomedical applications", *Journal of Optoelectronics and Advanced Materials*, Vol. 10, No. 8, August 2008, pp. 2151-2155.
- [12] Al-Bassam KS," The mineralogy and geochemistry of the marine sedimentary phosphate deposits of Iraq and other areas in the middle east", Ph.D. thesis, Wales University College Cardiff, Department of mineral exploitation, 1974.
- [13] Hossein Eslami, Mehran Solati-Hashjin, Mohammadreza Tahriri," Synthesis and Characterization of Hydroxyapatite Nanocrystals via Chemical Precipitation Technique",*Iranian Journal of Pharmaceutical Sciences*,Vol.4,No.2,2008,pp:127-134.
- [14] Wei Zheng M., "Preparation and characterization of tri calcium phosphate scaffolds with a Tunnel-like Macro-pores for Bone Tissue Engineering" Faculty of Built Environment and Engineering Queensland University of Technology, 2011.
- [15] Liga Berzina-Cimdina and Natalija Borodajenko, "Infrared Spectroscopy - Materials Science, Engineering and Technology", 2012.