

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin

A S Karim
College of Science Education
University of Sallahadin

Abstract

Samples of X%Al₂O₃ (X = 17.85, 28.05, 87.98 and 95.63) were prepared from Iraqi kaolin, after calcinations process, by the method of evaporation. From the temperature dependence of capacitance, the temperature dependence of dielectric constant are studied for the samples of annealed powders of various Al₂O₃ contents in the frequency range 1KHz – 1MHz.

The frequency dependent values of dielectric constant for the powder content 87.98% Al₂O₃ and 95.63%Al₂O₃ are found to be varies between 9.21 – 12.29 and 6.99 – 12.063, respectively. While for the others percentage of 17.85%Al₂O₃ and 28.05%Al₂O₃ powder content samples, it changes between 22.195 – 151 and 13.015 – 21.09 , respectively. These dependence are analyzed and discussed in details.

The annealing temperature effect on the dielectric constant are given for the frequency investigation of 10KHz. However, the annealing temperature transforms the structure and that consequently affects the dielectric constant. The dielectric constant found to be decreases with increasing the temperature for all the investigated samples from 17.85%Al₂O₃ to the 95.63%Al₂O₃.

Keywords : Dielectric constant, Al₂O₃ powder, annealing temperature

تأثير التردد والحرارة على ثابت عزل مسحوق X %Al₂O₃

المستخرج من كاؤولين العراقي

أيوب صابر كريم

كلية تربية العلوم - جامعة صلاح الدين

المستخلص

تم تحضير نماذج من X%Al₂O₃ بنسب (17.85, 28.05, 87.98 and 95.63 X) من كاؤولين العراقي بعد عملية التحميص و بطريقة التبخير . من الاعتماد الحراري للسعة , تم دراسة ثابت العزل للمسحوق المحمص لمختلف النسب من x% Al₂O₃ و تحت تأثير التردد في المدى 1KHz - 1MHz .

وجدت بأن الاعتماد الحراري لثابت العزل للمسحوق التي تحتوي على نسب Al₂O₃ 87.98 % و 95.63% Al₂O₃ هي 12.29 - 9.21 و 12.65 - 6.99 على التوالي . بينما لبقية النماذج التي تحتوي على نسب 17.85%Al₂O₃ و 28.05% Al₂O₃ فانها تتغير بين 151 - 22.195 و 21.09 - 13.015 على التوالي. تم تحليل ومناقشة هذه الاعتمادية بالتفصيل.

كذلك تم دراسة تأثير عملية تحميص على ثابت العزل عند التردد 10KHz . من تأثير حرارة التحميص وجدت بأن التركيب البلوري هي السبب الاساسي لتقليل قيمة ثابت العزل عندما للنماذج 17.85% Al₂O₃ الى 95.63 % Al₂O₃ .

Introduction

Ceramic suitable for use in capacitors are characterized by a high dielectric constant. In conventional ceramics, however, the dielectric constant has shown a strong dependence on temperature. The behavior of the capacitance with respect to temperature is quantified in a single term called the temperature coefficient of capacitance (hereafter referred to as TCC which is expressed in terms of parts per million (ppm/degree.C). Careful material selection and processing have made possible the development of dielectric ceramic bodies that have very small TCC's over a wide range of temperature. This phenomenon can occur when a multiphase body is formed in which each phase with a positive TCC is counterbalanced by one or more phases with an equivalently negative

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

TCC. Certain bodies in which this compensating effect is present have temperature coefficient of capacitance that are usually small and are known as Negative-positive-Zero or NPO bodies [Inventors, 1990] .

The demand for ceramics in the electrical industry has phenomenally both in quantity and quality during last and this century. Singer and Singer 1963 and Budnikov 1964, classified ceramic materials for electrical industry and their general properties. Graham and Tallen 1971 briefly classified and described the broad field of polycrystalline electrical insulators. Ceramic materials that satisfy the value of dielectric constant and dielectric loss index at 1 MHz, (≤ 30 and ≤ 0.03), respectively at 25 °C, would be classified as a good electrical insulators [Buchman, 1981 and Van vlack, 1964].

In the last fifty year, a great deal of assessment has been carried out in manufacturing electrical insulators. Bauer and Dietz, 1981, discussed the future needs for composite and porcelain electrical insulators. Other workers [Nortan, 1978; leda, and tanaka, 1986; and Roggen, 1990] outlined in some detail the development, which took place in the instrumentation and methods of studying such insulators.

The dielectric constants of comparably grown unpatterned films of Al₂O₃ has been measured and found to be 8.9 - 9 at various film thickness and measurement temperatures [Biercuk et al. 2003] .

Alumina is an important electro ceramic material with ultra-low dielectric constant ($\epsilon_r \sim 9.8$). Many papers have been published to report the origins of dielectric loss, which fall into two categories: intrinsic loss is dependent on the crystal structure and can be described by the interaction of the phonon with the ac electric field. The ac electric field alters the equilibrium of the phonon system and the subsequent relation is associated with the energy dissipation. Extrinsic losses are associated with imperfections in crystal structure, e.g., lattice disorder, point defects, dislocations, grain boundaries, random crystalline orientation, impurities, porosity and microcracks. Alford et al. have made a profound investigation of the extrinsic loss of polycrystalline alumina [Song et al.; 2007].

Rasin, F.A. in (1998) has been studied the dielectric properties for types of material rocks. The rocks were porcelanite, the major mineral, that constitute it, is OPAL-CT and the second is Ninivite rocks, the major mineral, that constitute it, is quartz. The dielectric constant of ceramic body is affected by changes in its composition, manufacturing technique

and density (porosity) as well as by testing factors including the effect of temperature and voltage frequency [Frank, 1962; Harrop, 1972].

In this work temperature dependence of capacitance, and factors affects X%Al₂O₃ capacitance are investigated. The effect of calcinations on dielectric properties of powder extracted from Iraqi kaolin will also be studied.. In addition, dielectric constant of X%Al₂O₃ with various powder contents at different frequency region will be discussed.

Experiments

A- X%Al₂O₃ materials and formation process

X%Al₂O₃ was chosen as a ceramic powder with various ratios , at various of X (X= 17.85, 28.05, 87.98 and 95.63), because it is one of the widely-used high dielectric constant powders. In this work, the Al₂O₃ powder with various contents of X, produced by evaporation method, from Iraqi Kaolin, which is an abundant material in Iraq. The agent solvent H₂SO₄ was used for materials extraction [Karim, 2006]. Samples were provided with 13mm diameter discs and 0.3822mm of average thickness.

B- Capacitor fabrication and characterization

A schematic view of the measurement technique is shown in Fig.(1) . Two parallel conductor, 12.002 mm in diameter was used to fabricate this capacitor so as one of them is fixed and the other is movable, their adjustment were controlled with a small coiled spring to allowed both the sample and the system expansion and also contraction throughout both heating and cooling. A two coiled short circuit heaters made from a copper wire with a diameter of about (0.5mm), with a use of (1.45-1.55) DC applied voltage.

To prevent the effects of the electromagnetic waves the heaters and wires used in the circuit were covered by a thin aluminum foil. Capacitance measurements C were performed by a programmable RCL meter at various frequencies in the temperature range (27-110) °C. The capacitor system was placed inside a thermally insulated cavity made of cork materials.

The test specimen and guard electrode are designed in such away that the sample diameter be larger than that of guarded electrode by at least 0.994mm. In these conditions the field distribution in the guarded area will be identical with that existing when vacuum is the dielectric, and the ratio between these two direct capacitance is the dielectric constant. One advantage of the RCL meter method is that, since the powder samples are in contact with metal electrodes, it is free from any influence of both the

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

electrodes and the electromagnetic effects on Alumina transition properties. The RLC digital starts by arranging the earth contacts for the capacitance to discharge any of the existent electromagnetic wave, throughout the measurements. The measuring frequency range were from 1KHz to 1MHz.

C- Accuracy, Precision and Calibration Concepts:

The thickness must be determined by measurements distributed systematically over the area of the specimen that is used in the electrical measurement. In the present work the thickness was measured using micrometer with an accuracy of $\pm 0.02\text{mm}$ and the average value is taken into account. In this field, one could take into account, that error calculation follows the rules defined by the American Nation Bureau of standards [Rasin, 1998]

Copper-constantan as thermocouple devices were chosen for the measure of samples temperature in the range of (27 - 110) °C. The copper constant thermocouple was calibrated by comparison the data readed from digital thermometer with that of the mercury thermometer where both are inside of a heated water and the detailed are given else where [Abbas, 2005] . The LCR- meter was calibrated using a built-in calibration software, followed by using standard capacitors and resistors. The sample handling precaution are in accordance with ASTM D 1371, [Rasin, 1998]. The measuring frequency range is sufficient to satisfy the requirement for dielectric measurements in the present work.

THERMALLY INSULATED

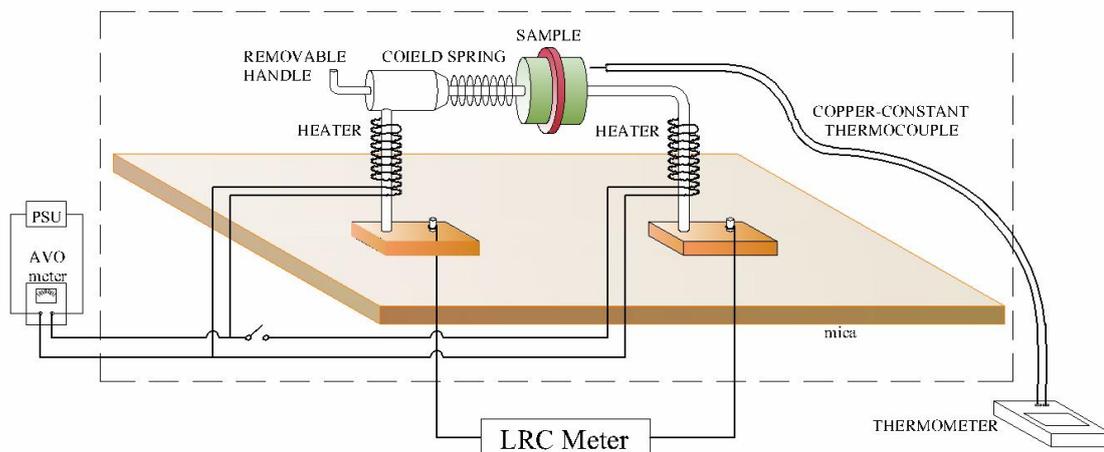


Fig: (1): Schematic diagram of the capacitor system and dielectric measurement.

Temperature dependence of X%Al₂O₃ capacitance

Generally, capacitance of capacitors can be expressed as

$$C = \epsilon \frac{A}{t} = \epsilon_0 k \frac{A}{t}, \quad (k = \frac{\epsilon}{\epsilon_0}), \dots\dots\dots (1)$$

C is capacitance, k is relative dielectric constant, ε₀ and ε are vacuum and dielectric material's permittivity, t and A are the thickness and area of a dielectric material. Based on the above equation, the relation between temperature dependence of capacitance and dielectric constant can be expressed as [Hyun et al., 2005]

$$\frac{1}{C} \cdot \frac{dC}{dT} = \frac{A}{t} \frac{1}{k} \cdot \frac{dk}{dT} \dots\dots\dots (2)$$

Where { $\frac{1}{C} \cdot \frac{dC}{dT}$ } is defined as temperature coefficient of capacitance (TCC) and

{ $\frac{A}{t} \frac{1}{k} \cdot \frac{dk}{dT}$ } is defined a temperature dependence of dielectric constant (TCK). Because thermal expansion coefficient of metal electrodes is in the range of (~10⁻⁶/K) and the dimension of the metal electrode increase uniformly as the sample temperature increases it is possible to assume that the temperature dependence of electrode area A and thermal expansion coefficient of Al₂O₃ samples thickness (~10⁻⁶/K) are negligible [SAINT, 2005]. However, powder contain Al₂O₃ annealed at temperatures higher than 80° C and then pressing under a pressure of about 10 tone will produce a sintering form material where it was originally in a pores state. As a result, the porosity is so much lowest for the samples so as their effects also could be neglected, then, the temperature dependence of capacitance of Al₂O₃ is defined by

$$(TCC) = (TCK) \dots\dots\dots (3)$$

Therefore, the main factor of temperature dependence of x%Al₂O₃ capacitance is determined by changes of dielectric constant of x%Al₂O₃ s only. Figs. 2(a), (3a), (4a), (5a) show temperature dependence of capacitance. From these values, dielectric constants for X%Al₂O₃ composites were calculated and plotted as shown in Figs. 2(b), 3(b), 4(b), 5(b).

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

From Fig.2(a)and (b), show the temperature dependence for both capacitance and dielectric constant of 17.85%Al₂O₃. Their values decreases in the range from 30 °C to 60 °C and increased in between 90 to 110 °C for both 1KHz and 10KHz. The reason for this could be due to the dielectric constant at low frequencies which can be attributed to molecular polarization of the asymmetric pyridine group in Al₂(SO₄)₃.18H₂O [Karim, 2006]. At high frequencies since these groups can not maintain the alignment in the alternating field [Wyllie, 1960] then only electronic polarization exists. Calcinations of sample's at 600°C, causes to a removal of hydrated polarization, then both capacitance and dielectric constant remains slightly changeable throughout the investigated temperature range (30-110 °C) as indicated in Figs.3(a), (b). In which however, both of the dependence affected strongly by the applied frequency and they are increase systematically with temperature. It is clear from the two Figures of 2 and 3, the increase of Al₂O₃ content will make both the temperature and frequency depend for both capacitance and dielectric constant in a systematical form. However, the occurrence of the dehydroxylation process at 600°C may probably be the reason. The explanation is the formation of Al₂(SO₄)₃ which a weight loss signals break-up. The dependence of loss factor, values with temperature and for three different frequencies are given in Figures 2c and.3c [Karim, 2006].

Fig. 3(b) shows the variation of dielectric constant (ϵ_r) with temperature for 28.05%Al₂O₃ at different frequencies. Dielectric constant increase slightly with temperature at 10KHz, 100KHz, while at 1MHz the amount of increasing approximately changes more than that occurs for 10KHz, 100KHz. At high frequencies, since the groups can not maintain the alignment in alternating field, only electronic polarization exist. Similar results however, been observed in the case of (Al₅Y₃O₂) glass ceramics and other conventional number ceramic materials [Sutton, 1989]

Fig.(4) shows changes the capacitance, dielectric constant and loss factor $\tan\delta$ vs. temperature at various frequencies for the 87.98% Al₂O₃ powder content. As the temperature elevated up to 60 °C, both capacitance and dielectric constant decreased while loss factor increases. Above 60 °C, the change rates started to remain constant. This may be due to maintaining phase transition for gamma-Al₂O₃ powder [Alford, 1996]. A higher amount of capacitance and dielectric constant was also observed for 1MHz in comparison to that of the frequencies of 10KHz and 100KHz.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

Fig.5 shows the change of capacitance , dielectric constant and loss factor vs. temperature for 95.63% Al₂O₃ power contents at various frequencies. For this constinent, the capacitance, dielectric constants and loss factor are changes very slightly through the temperature range investigated. However, the crystal phase structure in this case remain as alpha-Al₂O₃ throughout all the temperature range investigated.

The dielectric constant and loss factor dependence on the applied frequency under the effect of annealing temperatures were also investigated. The curve shape in both Figures of 6 and 7 are indicated the increase of molecular polarization contributes, especially in the frequencies range of 10 – 200 KHz [Rasin, 1998].

Fig. 8 and Fig.10 shows dependence of dielectric constant with the annealing temperatures as well as with that of Al₂O₃ percentage powder content samples, respectively. As shown from these two indicated figures , the dielectric constant for the as-synthesised sample, dried at 80 °C for 24h of 17.85% Al₂O₃ and for annealing at 600 °C of 28.05% Al₂O₃ at 10KHz are (151.559) and (13.015), respectively. This dielectric constant reduction is also observed for 87.98% Al₂O₃ and 95.63% Al₂O₃ powder contents. The dielectric constant for these two powder contents at the annealing temperatures 1000 and 1200°C and at the frequency of 10 KHz are (11.045) and (6.995), respectively. The effective dielectric constant of X% Al₂O₃ powder content is linearly proportional in the temperature range from 80 °C to the 1000 °C for values of X from 17.85% Al₂O₃ to 87.98% Al₂O₃ . Above this range, the relaxation expected to increase more strongly which give a more dielectric relaxation. Therefore the dielectric constant reduction of 87.98% Al₂O₃ and of 95.63% Al₂O₃ is mainly expected to be due to a phase transformation from gamma alumina at 1000 °C to that of alpha alumina at 1200 °C [Karim, 2006]. However, the above explanation can also be used to explain the loss factor tanδ, given in Fig.9.

However, the dielectric constant of 87.98% Al₂O₃ and 95.63% Al₂O₃ powder contents varies between 9.21 – 12.29 and 6.99 – 12.063, respectively, at the range of frequencies 10KHz, 100KHz and 1MHz at 30 °C, as shown in Figs. 4(b) and 5(b) and Tab.1 . However, at the same range of frequencies for the other percentages 17.85% Al₂O₃ and 28.08% Al₂O₃ powder samples its change between 22.195 – 151 and 13.015 – 21.09, respectively, that is due to the dominates of Al₂(SO₃).16H₂O and Al₂(SO₃) [ayoub, 2006]. While for the first two

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

Al₂O₃ percentage samples the phase structures are γ and α - alumina [ayoub, 2006].

Table1: Dielectric constant for X%Al₂O₃ various frequencies at room temperature.

Annealing temp.	X%Al ₂ O ₃	10kHz	100 kHz	1MHz
as synthesised	17.85	151.5	22.1955	33.519
600 °C	28.05	13.0152	13.7856	21.0965
1000 °C	87.98	11.0454	9.21157	12.2977
1200 °C	95.63	6.99586	10.5375	12.063869

Conclusion

The alumina extracted from Iraqi Kaolin by evaporation method, at various Al₂O₃ powder contents, are suitable to use as an insulator ceramic material. Annealing temperature is controls the amount of dielectric constant as well as the loss factor of X%Al₂O₃ content ceramics . The material also suitable to use as a high and low frequency capacitance.

Acknowledgement

I acknowledge the college of Science Education in this university for their financial assistance. I am very thankful to Dr. M. S. Omar at the physics department, college of science , university of Salahaddin, for his technical help and his primary reading the paper.

Reference

- Abbas, P.A. (2005) "Physical properties of N-type Gap single crystal semiconductor compound," Ph. D. Thesis, Salahaddin University, Erbil.
- Biercuk J. M ; Monsma J. D. and Marcus M.C. , (2003), Low temperature at mic-layer- position lift- off method for microelectronic and nonolectronic applications," Applied phys Letters Vol. 83, No.12.
- Budnikov, P.P. 1964 "The Technology of Ceramics and Refractories, part III, M.I.T. Press, Cambrige.Ch1x.pp.500-565"
- Buchman, R.C.(1981) "Properties of ceramic insulators-dielectric properties, Ceramic Materials for Electronics processing; properties and applications" (Buchanan, R, C. ED.), Mercel Inc. New York.
- Bauer, E. and Dietz, H. (1981) Porcelain and composite long-rod insulator-A solution for future line requirements, IEEE Transactions on Electrical Insulation , Vol.E-16, No.3 p209-219.
- Frank, M.C. (1962) " Insulating Materials for Design and Engineering Practice," John Wiley and Sons, Inc.New York.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

- Graham, H.C, and Tallan, N.M. (1971) Polycrystalline insulators. Physics of electronic Ceramics, part A(L.L. Hench and D.B. Dove ed.), Marcel Dekker, Inc, New York .
- Harrop, P.J. (1972) Dielectrics. Butterworth & Co. (Publishers) Ltd. London Butterworths) p.50
- Hyun, G.J.: Lee, S.: Cho, D.S. and Paik, W.K. (2005) “ Frequency and Temperature Dependence of Epoxy/BaTiO₃ Composite Embedded Capacitor Films (ECFs) for Organic Substrate,” Components and Technology conference,pp 1241-1247.
- Inventors: Bardhan; Pronob (Corning, NY); Bartholomew; Roger F. (Painted Post, NY; Trotter, Jr.; Donald M. (Newfield, NY);Yu; Chyang J.(Painted Post, NY), (1990) “Capacitors and high dielectric constant ceramics therefor” United State Patent 4978646, View Patent Images.
- Ieda, M. and tanaka, T. 1986 Recent forty-years activity in electrical insulators, IEEE Transactions on Electrical Insulation,vol.EI-21,No.6,pp.823-829.
- Karim.S. A.(2006) “The Investigation of the γ -alumina powder extracted from Iraqi kaolin” Ph.D. Thesis, Baghdad University, Baghdad.
- Nortan, F.H.(1978) “Cycles in ceramic history. Ceramic Processing before Firing, ” (C.Y. Onoda, jr. and LL. Hench ed.) A Wiley Interscience Publication. John Wiley & Sons ,Inc .New York.
- Rasin, A.F. (1998) “The use of Iraqi Siliceous Rocks as Electrical Insulators in Industry,” Ph.D. Thesis, Saddam University, Baghdad.
- Roggen,A.V. (1990) “An overview of dielectric measurement, ” IEEE Transactions on Electrical Insulation,Vol.25, No.1, pp.95-105.
- Song, X. K.; Wu, Y. S. and Chen, M. X. .(2007) “Effects of Y₂O₃ addition on microwave dielectric characteristics, ” Mater. Lett. Available online at www.sciencedirect.com.
- Singer, F. and Singer, S.S. (1963) “ Industrial Ceramics”. Chapman and Hall LTD, London.
- Sutton, H.W. (1989) Am. Ceram. Soc. Bull 68,376
- Wyllie, G. (1960) “Theory of polarization and absorption in dielectrics; an introductory survey, ”. Progress in Dielectrics, vol.2(J. B. Birks "General ed.' and J. H. Schulman"American ed. ") Heywood and Company Ltd. London.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

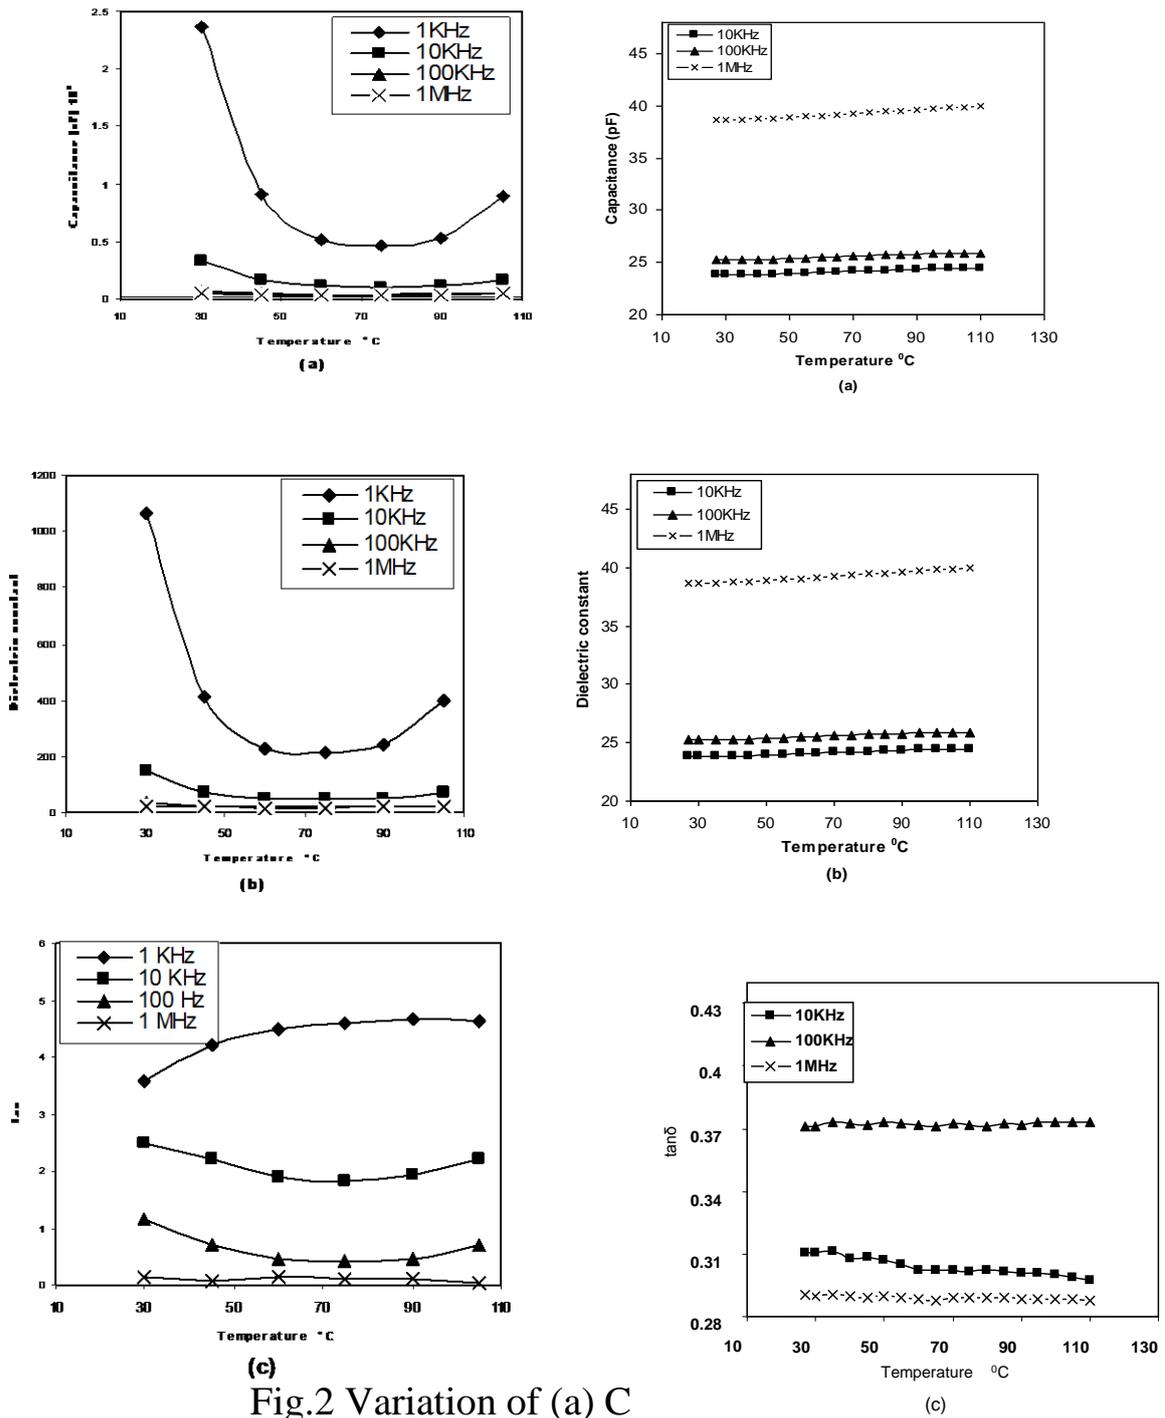


Fig.2 Variation of (a) C

Fig.3 Variation of (a) capacitance, (b) dielectric constant, and (c) loss factor vs. temperature for constant, and (c) loss factor vs temperature for 17.85% Al₂O₃ powder contents. 28.05% Al₂O₃ powder contents.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

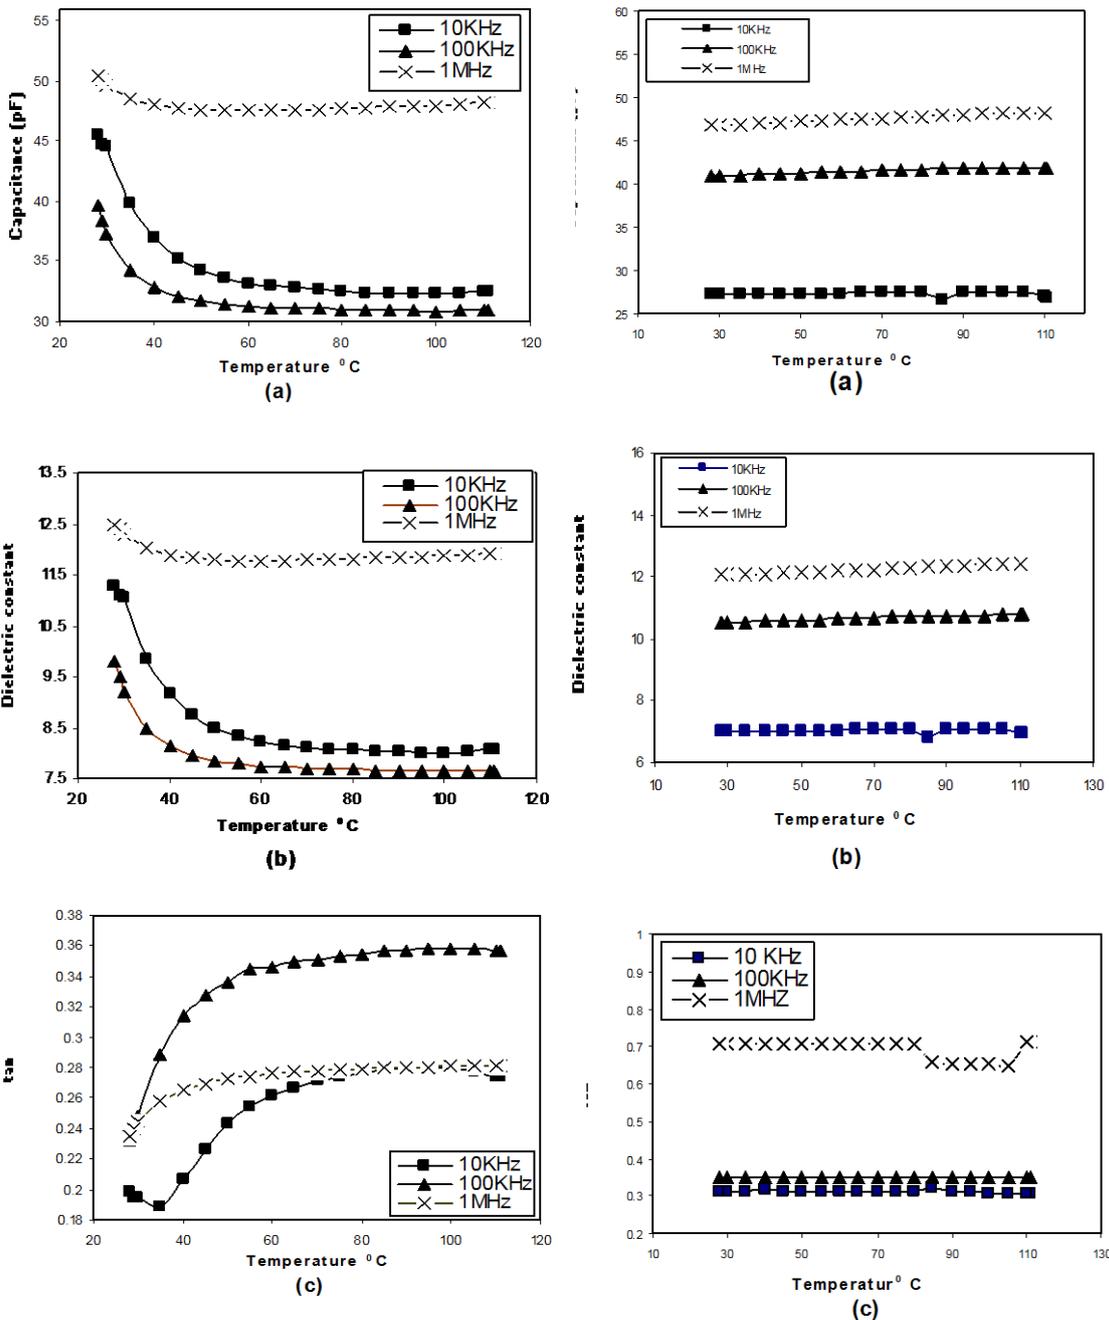


Fig.4 Variation of (a) Capacitance, (b) dielectric constant, and (c) loss factor vs. temperature for 87.98% Al₂O₃ powder contents. Fig.5 Variation of (a) Capacitance, (b) dielectric constant, and (c) loss factor vs. temperature for 95.63% Al₂O₃ powder contents.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

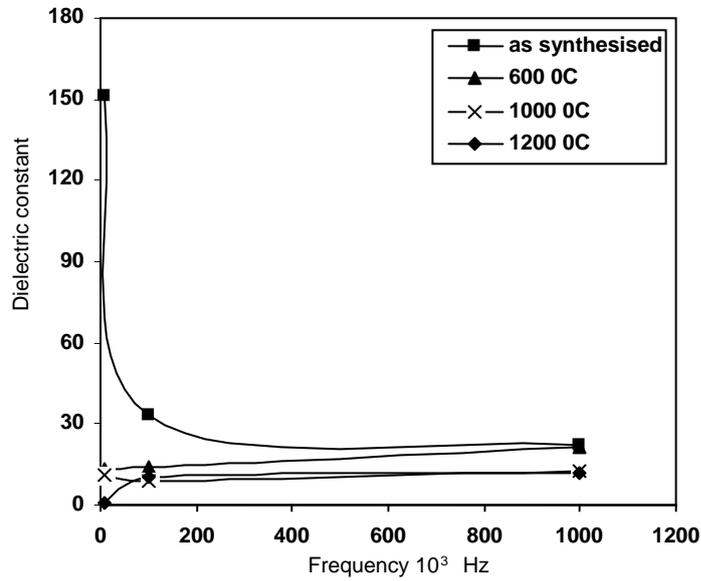


Fig.6 dielectric constant versus frequency for various annealing temperatures

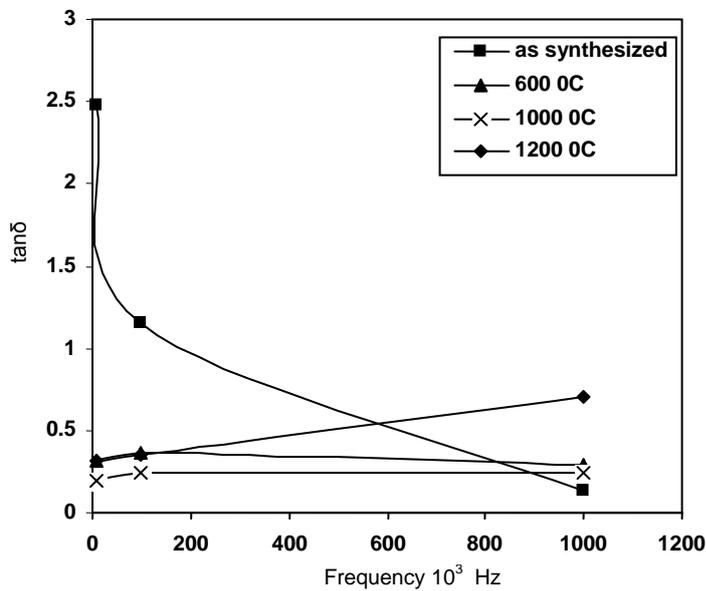


Fig.7 Loss factor versus frequency for various annealing temperatures.

The Effects of Frequency and Temperature on the Dielectric Constant of X%Al₂O₃ Powder Extracted From Iraqi Kaolin.....A S Karim

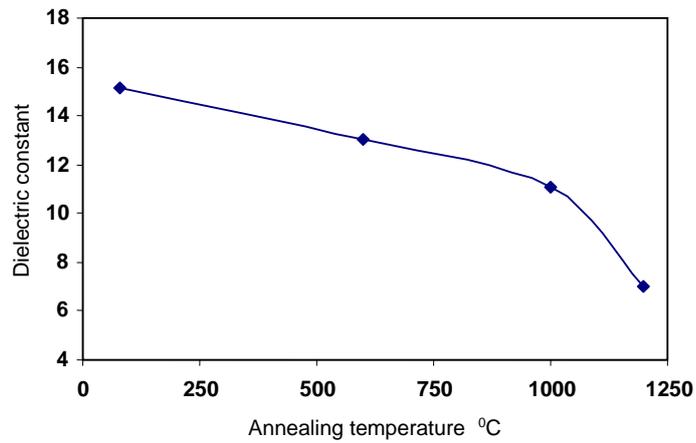


Fig.8 Dielectric constant versus annealing temperature at 10 KHz at room temperature.

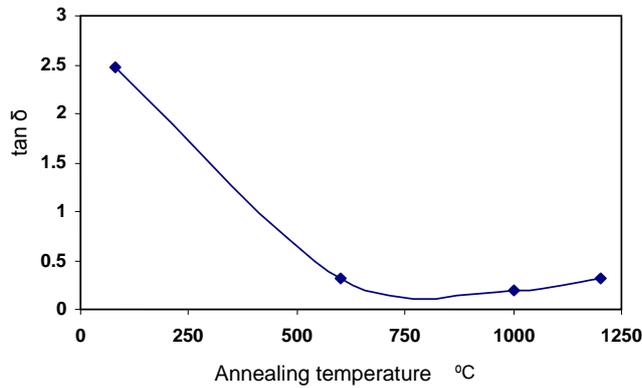


Fig.9 Loss factor versus annealing temperature at 10 KHz

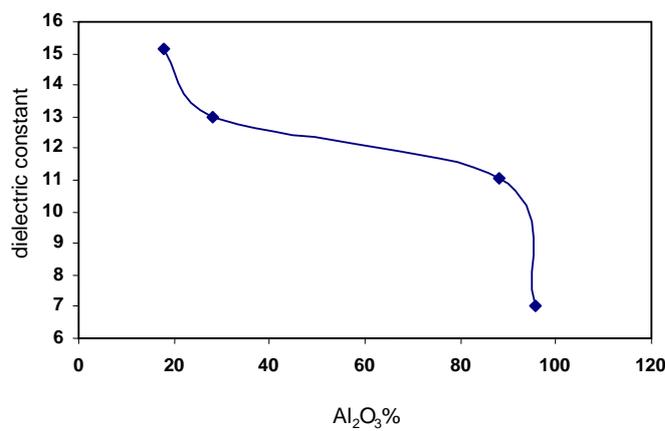


Fig.10 Dielectric constant versus Al₂O₃ % at room temperature